



# International Journal of Engineering Research and Science & Technology

ISSN : 2319-5991  
Vol. 2, No. 4  
November 2013



[www.ijerst.com](http://www.ijerst.com)

Email: [editorijerst@gmail.com](mailto:editorijerst@gmail.com) or [editor@ijerst.com](mailto:editor@ijerst.com)

Research Paper

# CHARACTERIZATION OF HYBRID POLYMER COMPOSITES

S Bhargavi Devi<sup>1\*</sup>, Syed Altaf Hussian<sup>1</sup>, K Tirupathi Reddy<sup>1</sup>  
and K Sudha Madhuri<sup>1</sup>

\*Corresponding Author: **S Bhargavi Devi**, ✉ [sbhargavidevi@gmail.com](mailto:sbhargavidevi@gmail.com)

Bamboo/Glass fiber reinforced polymer composites are replacing conventional metal alloys owing to their eco-friendly nature. Natural fibers as reinforcement offer number of advantages than traditional synthetic fibers. This paper aims to determine the mechanical properties namely, Tensile Strength (TS), Impact Strength (IS), Flexural Strength (FS), Hardness, Chemical resistance and water absorption of hybrid composites reinforced with Bamboo/Glass fiber. The Treated bamboo fibers are mixed with the glass fiber in the proportion of 1:1, in order to reinforce in epoxy resin with different fiber lengths (5, 10, 15 mm) and fiber weight fractions of (20%, 30%, 40%). Experiments are planned according L9 orthogonal array in Taguchi's design of experiments. The control parameters considered were Fiber Length (F) and percentage Fiber weight fraction ( $V_f$ ). In this work an attempt has been made to model the mechanical properties through Response Surface Methodology (RSM). Analysis of Variance (ANOVA) is used to check the validity of the model. The results indicated that the developed quadratic models are suitable for the prediction of mechanical properties of the Bamboo/glass fiber reinforced epoxy composites. The experiment result reveals that tensile strength, flexural strength and hardness were decreased with increase of fiber length but impact strength increased with increase of fiber length.

**Keywords:** Bamboo fiber, Chemical resistance, Glass fiber, Hybrid composites, Mechanical properties

## INTRODUCTION

A composite is usually made up of at least two materials out of which one is the binding material, also called matrix and the other is the reinforcement material (fiber, Kevlar and whiskers). The advantage of composite materials over conventional materials are largely from their

higher specific strength, stiffness and fatigue characteristics, which enables structural design to be more versatile. By definition, composite materials consist of two or more constituents with physically separable phases. However, only when the composite phase materials have notably different physical properties it is recognized as

<sup>1</sup> Department of Mechanical Engineering, RGM College of Engineering & Technology, Nandyal-518501, India.

being a composite material. Composites are materials that comprise strong load carrying material (known as reinforcement) imbedded in weaker material (known as matrix). Reinforcement provides strength and rigidity, helping to support structural load. The matrix or binder (organic or inorganic) maintains the position and orientation of the reinforcement. Significantly, constituents of the composites retain their individual, physical and chemical properties; yet together they produce a combination of qualities which individual constituents would be incapable of producing alone. The reinforcement may be platelets, particles or fibers and are usually added to improve mechanical properties such as stiffness, strength and toughness of the matrix material. Thermoplastics occupy only a small percentage of the advanced composite market, while other and epoxy thermoset materials contribute to more than 70%. Epoxy resins, the most important matrix polymer when it comes to high performance. Natural fibers such as bamboo, coir, jute, flax, sisal etc., are low density fibers available at low cost. Natural fibers are renewable and also easily biodegradable. In spite of having several merits, natural fibers show lower modulus, lower strength and poor resistance when compared with the composites reinforced with synthetic fibers such as glass, carbon and aramid. To overcome these limitations and to obtain great diversity of material properties, hybrid composites have been conceived where in two or more fibers are reinforced in a single matrix. Its combination with glass fibers gives an advanced composite with properties like low weight, good mechanical properties and tribological properties. These materials make very attractive for use in aerospace applications. A

rough estimate has it that for every unit of weight reduction in aircraft, there is a considerable less considerable fuel consumption or higher load capacity and hence material offers material saving. Due to low density around  $1.3 \text{ g/cm}^3$ , good adhesive and mechanical properties, epoxy resins become a promising material for in the transportation industry, usually in the form of composite materials. The performance of these composites not only depends on the selection of its components, but also on the interface between fiber and resin. Sometimes it is necessary to modify the matrix and reinforcement for specific properties. Due to low density natural fibers are widely used as reinforcing agent as it is high biodegradability. Natural fibers are largely divided into two categories depending on their origin: plant based and animal based. Therefore, natural fiber can serve as reinforcements by improving the strength and stiffness and also reducing the weight of resulting Biocomposites materials, although the properties of natural fibers vary with their source and treatments.

Ashok Kumar *et al.* (2010) studied on epoxy hybrid composites reinforced with sisal/glass fiber on frictional co-efficient, impact, hardness and chemical resistance as function of fiber length. Hence proved that, mechanical properties were optimized at 2 cm fiber length.

Raghavendra Rao *et al.* (2011) studied on effect of frictional and impact properties, dielectric strength, chemical resistance and SEM analysis of reinforced Bamboo/ Glass fiber Epoxy based Hybrid Composites.

Girisha *et al.* studied on epoxy hybrid composites reinforced with sisal/coconut natural fibers on water absorption and mechanical properties.

## MATERIALS AND METHODS

High performance epoxy resin LY 556 and the curing agent hardener HY 951 system were used as the matrix. Bamboo fibers were procured from Tripura state of India in the dried form. Some of these fibers were soaked in 3 moles of NaOH solution for 30 min to remove any greasy material and hemi cellulose, washed thoroughly in distilled water and dried under the sun for one week. The glass chopped strand mat was used in making the hybrid composite percentage.

## RESPONSE SURFACE METHODOLOGY

Response Surface Methodology (RSM) is a collection of mathematical and statistical techniques that are useful for modeling and analysis of problems in which a response of interest is influenced by several variables and the objective is to optimize this response, Montgomery (1991). Palani Kumar and Karthikeyan (2007) have developed a second order mathematical model using RSM to predict surface roughness on machining of Al/Sic particulate composite material. In the present work, second order RSM based mathematical model of mechanical properties have been developed. In many engineering fields, there is a relationship between an output variable of interest 'y' and a set of controllable variables  $\{x_1, x_2, \dots, x_n\}$ . In some systems, the nature of relationship between y and x values might be known.

Then, a model can be written in the form

$$Y = f(x_1, x_2, \dots, x_n) + \varepsilon \quad \dots(1)$$

where  $\varepsilon$  represents noise or error observed in the response 'Y'


If we denote the expected response be  $E(Y) = f(x_1, x_2, \dots, x_n) = \hat{Y}$  is called response surface. The first step is to find suitable approximation for the true functional relationship between y and set of independent variables employed usually a second order model is used in RSM.

$$\hat{Y} = \beta_0 + \sum_{i=1}^n \beta_i x_i + \sum_{i=1}^n \beta_{ij} x_i^2 + \sum_{i=1}^n \beta_{ij} x_i x_j + \varepsilon \quad \dots(2)$$

where  $\beta_0, \beta_i$  and  $\beta_{ij}$  are the regression coefficients and  $n$  is the number of model parameters (i.e., process parameters). The  $\beta$  coefficients, used in the above model can be calculated by means of using least square method. The second-order model is normally used when the response function is not known or nonlinear.

## COMPOSITE MANUFACTURING

Hybrid laminates of Bamboo and glass fiber were prepared by simple hand layup technique in a wooden mold at room temperature. For making the composite, a molding box was prepared with wood as per the ASTM standards with 200 mm X 100 mm X 5 mm mould cavity. The impregnated layers were stacked one over the other in the mold and pressed upto the removal, uniform thickness was achieved by using spacers of desired thickness between the mold plates. Figure 1 shows the stacking sequence used in the laminate preparation. Exhaustive literature review on mechanical behavior of polymer composites reveals that parameters, viz., fiber length and fiber volume fraction, etc., largely influence the mechanical behavior of polymer composites. Composite materials were fabricated using Taguchi's L9 orthogonal array in the Design of Experiments (DoE) (Noorunnisa et al., 2009), which needs 9 runs and has 8 degrees of

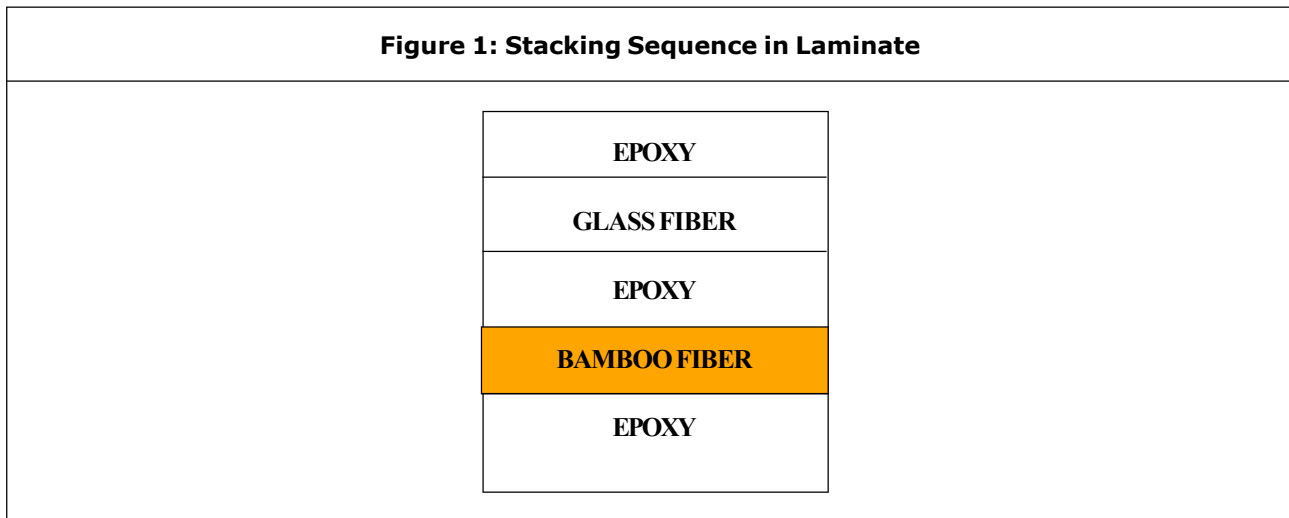

freedom. The control parameters used and their levels chosen are given in Table 1

### PREPARATION OF TEST SPECIMENS

Tensile testing samples were prepared like dumbbell shapes as per the ASTM D 638-02a (165 mm x 20 mm x 5 mm). The specimens were tested by Universal Testing Machine (UTM). The tension test is generally performed on flat or round specimens (Raghavendra *et al.*, 2011). A uniaxial load is applied through the ends. Ultimate tensile strength is the force required to fracture a material. The tensile strength can be experimentally determined by the given formula.

$$\text{Tensile Strength} = \frac{\text{Maximum tensile load applied}}{\text{Original cross section area}} = \frac{P_{MAX}}{A}$$

The ultimate tensile strength  $P_{MAX}$  can be determined by the stress strain graph. The unit

used for tensile strength is N/m<sup>2</sup>. In each case 3 samples were tested and average value is recorded.

### FLEXURAL TEST

Flexural strength was determined using universal testing machine equipment. The specimen are prepared as per ASTM D790-03, the test speed was maintained at 5 mm/min, at a temperature 22°C and humidity 50%. According to ASTM D 790-03 the flexural test specimen dimensions are 150 mm X 20 mm X 5 mm. In each case 3 samples were tested and average value is recorded.

### IMPACT TEST

The Impact strength of notched specimens was determined by using an impact tester according to ASTM D 256- 04 (65 mm x 10 mm x 5 mm). In each case 3 samples were tested and average value is recorded.

<b>Table 1: Control Parameters and Their Levels</b>			
<b>Fiber weight fraction(<math>W_f</math>), %</b>	<b>Level 1</b>	<b>Level 2</b>	<b>Level 3</b>
	20	30	40
<b>Fiber length(<math>F_l</math>), mm</b>	5	10	15

## HARDNESS

According to ASTM D 785, the Rockwell hardness tester is used for testing hardness of the composites.

The type of indenter used is Ball indenter.

Diameter of the ball indenter = 0.25 inches  
=0.635 cm.

Maximum Load applied is 60 kg and L-scale is used.

## CHEMICAL RESISTANCE TEST

The chemical resistance testing on laminates is performed in accordance with ASTM D543.

According to ASTM standards the specimen dimensions are 5 mm X 5 mm X 5 mm.

The chemicals used in this testing are 5% Sodium carbonate (Na<sub>2</sub>CO<sub>3</sub>), 5% Hydrochloric acid (HCl), 5% Pure Acetic acid.

## RESULTS AND DISCUSSION

In this work composite material is fabricated using hand layup method. The experiments were conducted as per the Taguchi's orthogonal array L<sub>9</sub> design of experiments. The four mechanical properties selected for this investigation is tensile strength, Impact strength, Flexural strength and hardness. The experiment results are modeled using RSM and empirical model has been

developed. Table 2 shows the summary of models for the three responses.

Where Vf is fiber volume fraction (%) and Fl is fiber length (mm)

The statistical testing of the developed mathematical models was done by Fisher's statistical test for the analysis of variance (ANOVA). As per ANOVA, if the calculated value of F-ratio of the regression model is more than the standard tabulated value of the F-table for a given confidence interval, then the model is adequate within the confidence limit. The results of ANOVA at 95% confidence interval are presented in Table 3 and it is found that the developed mathematical models are highly significant at 95% confidence interval as F-ratio of all three models is greater than 9.01 (Table 3).

The coefficient of determination (*R*<sup>2</sup>) is also determined to test the goodness-of fit of the mathematical model, which provides a measure of variability in the observed values of response and can be explained by the controlled process parameters and their interactions. The *R*<sup>2</sup> values of the developed models are given in Table 3, which clearly indicate the excellent correlation between the experimental and the predicted values of the responses. Adding a variable to the model will always increase *R*<sup>2</sup>, regardless of whether the additional variable is statistically

**Table 2: Model Summary of Mechanical Properties**

Measure of Performance	Model Expression	R <sup>2</sup>	Adj (R <sup>2</sup> )
Tensile strength(MPa)	145 - 2.42 W <sub>f</sub> - 17.8 F <sub>l</sub> + 0.100 W <sub>f</sub> *W <sub>f</sub> + 1.13 F <sub>l</sub> *F <sub>l</sub> - 0.278 W <sub>f</sub> *F <sub>l</sub>	98.5%	96.1%
Impact strength(KJ/m)	13.3 - 0.235 W <sub>f</sub> - 1.57 F <sub>l</sub> + 0.00013 W <sub>f</sub> *W <sub>f</sub> + 0.0473 F <sub>l</sub> *F <sub>l</sub> + 0.0220 W <sub>f</sub> *F <sub>l</sub>	94.7%	85.9%
Flexural strength(Mpa)	876 - 24.2 W <sub>f</sub> - 74.3 F <sub>l</sub> + 0.225 W <sub>f</sub> *W <sub>f</sub> + 2.40 F <sub>l</sub> *F <sub>l</sub> + 0.700 W <sub>f</sub> *F <sub>l</sub>	98.0%	94.7%
Hardness	55.8 + 1.99 W <sub>f</sub> - 4.34 F <sub>l</sub> - 0.0295 W <sub>f</sub> *W <sub>f</sub> + 0.262 F <sub>l</sub> *F <sub>l</sub> - 0.0315 W <sub>f</sub> *F <sub>l</sub>	95.2%	87.1%

**Table 3: ANOVA Results for Mechanical Properties of Composite Materials, Viz., Tensile Strength, Impact Strength, Flexural Strength and Hardness**

Response	Sum of Squares		Degree of Freedom		Mean Square		F-ratio
	Regression	Residual	Regression	Residual	Regression	Residual	
Tensile strength	4894.99	73.13	5	3	979.00	24.38	40.16
Impact strength	7.8268	0.4376	5	3	1.5654	0.1459	10.73
Flexural strength	25519.3	518.7	5	3	5103.9	172.9	29.52
Hardness	118.829	6.051	5	3	23.766	2.017	11.78

significant or not. In this discussion including unnecessary terms,  $R^2$  can be artificially high. Unlike  $R^2$ , adjusted  $R^2$  will often decrease, when unnecessary terms are added to the model.

Adjusted  $R^2$  will be taken into consideration, when the number of independent variables included in the model in the model. Hence, adjusted  $R^2$  is more appropriate than  $R^2$  for comparing models with different number of independent variables. When  $R^2$  and adjusted  $R^2$  differ dramatically, there is a good chance that non-significant terms have been included in the model.


From the models, it was revealed that the coefficient of determination ( $R^2$ ) is more than 95% in all the cases, which shows high correlation exists between the model and experimental values.

### Tensile Strength

The tensile strength is a predominant property in processing of composite materials. The influence of constituent Phases on the TS of hybrid composite can be studied by using Response graph and response table. Figure 2 shows the effect plot for tensile strength. From the graph it is inferred that, the observed tensile strength is higher at the fiber length of 5 mm than at 15 mm and 10 mm. It is also observed that tensile strength slightly increases with increase in fiber weight fraction. From the response Table 4 shows the effect of constituent phases on tensile strength. From the response table, it can be asserted that the fiber volume fraction is the main parameter which affects the tensile strength of the composite material.

**Table 4: Response Table for Tensile Strength**

Level	Fiber Weight Fraction(Wf)%	Fiber Length (FI), mm
1	33.89	65.96
2	31.85	19.72
3	49.80	29085
Delta	17.95	46.23
Rank	2	1

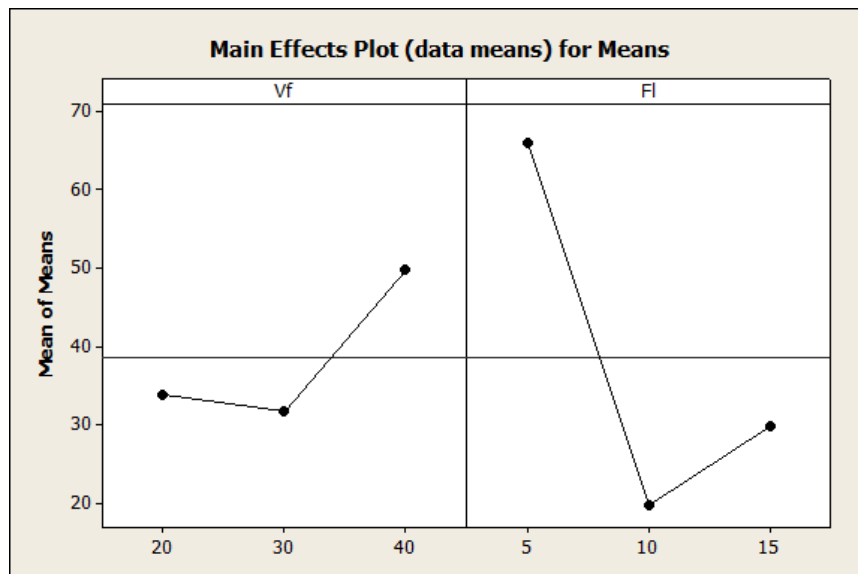**Figure 2: Main Effect Plots for Tensile Strength**

### Flexural Strength

The flexural strength is a predominant property in processing of composite materials. It is more influenced by fiber length (FI) and fiber weight fraction (Wf). The influence of the amount of constituent phases on flexural strength of the bamboo/glass fiber reinforced Hybrid composites can be studied by using Table 5 and Figure 3. From the graph it is inferred that, the observed flexural strength of the composite material is high at low fiber weight fraction as compared to high fiber volume fraction. The experimental results indicated that the flexural strength of the composite material is higher at lower fiber length. From the response table is asserted that the fiber weight fraction is the main parameter which affect the flexural strength of the bamboo/glass fiber reinforced Hybrid composites.

### Impact Strength

The impact strength is a predominant property in processing of composite materials. It is more


influenced by fiber length (FI) and fiber weight fraction (Vf). The influence of the amount of constituent phases on impact strength of the bamboo/glass fiber reinforced Hybrid composites can be studied by using Table 6 and response Figure 4. From the graph it is inferred that, the observed impact strength of the composite material is high at low fiber volume fraction as compared to high fiber weight fraction. The experimental results indicated that the Impact strength of the composite material is higher at higher fiber length. From the response table is asserted that the fiber length is the main parameter which affect the impact strength of the bamboo/glass fiber reinforced Hybrid composites.

### Hardness


The Hardness is a predominant property in processing of composite materials. It is more influenced by fiber length (FL) and fiber weight fraction (Wf). The influence of the amount of constituent phases on hardness of the bamboo/glass fiber reinforced Hybrid composites can be



<b>Table 5: Response Table for Flexural Strength</b>		
Level	Fiber Weight Fraction(Wf)%	Fiber Length (Fl), mm
1	178.33	170.00
2	95.33	43.67
3	48.33	108.33
Delta	130.00	126.33
Rank	1	2

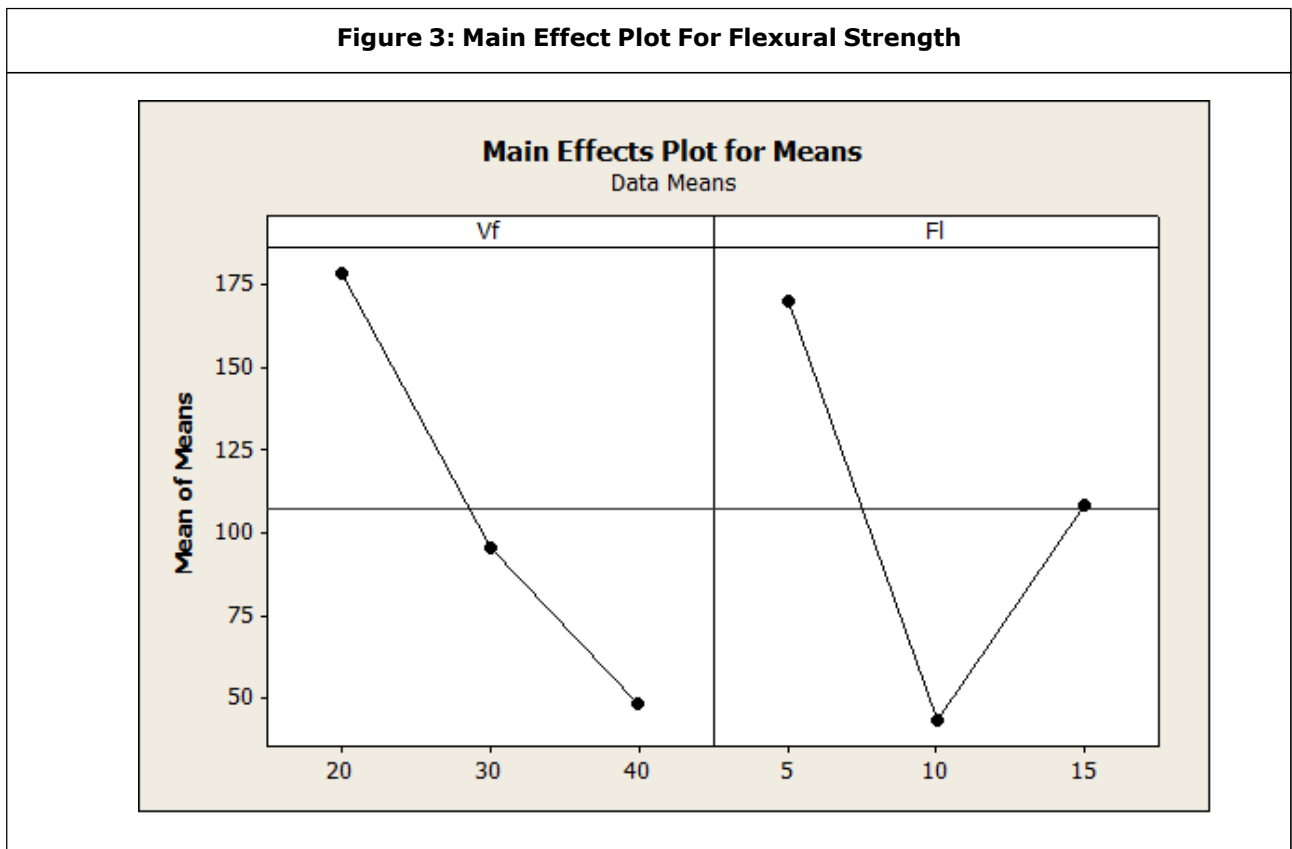

<b>Table 6: Response Table for Impact Strength (IS)</b>		
Level	Fiber Volume Fraction(Vf)%	Fiber Length (Fl), mm
1	2.813	2.970
2	2.724	1.947
3	2.667	3.290
Delta	0.147	1.343
Rank	2	1

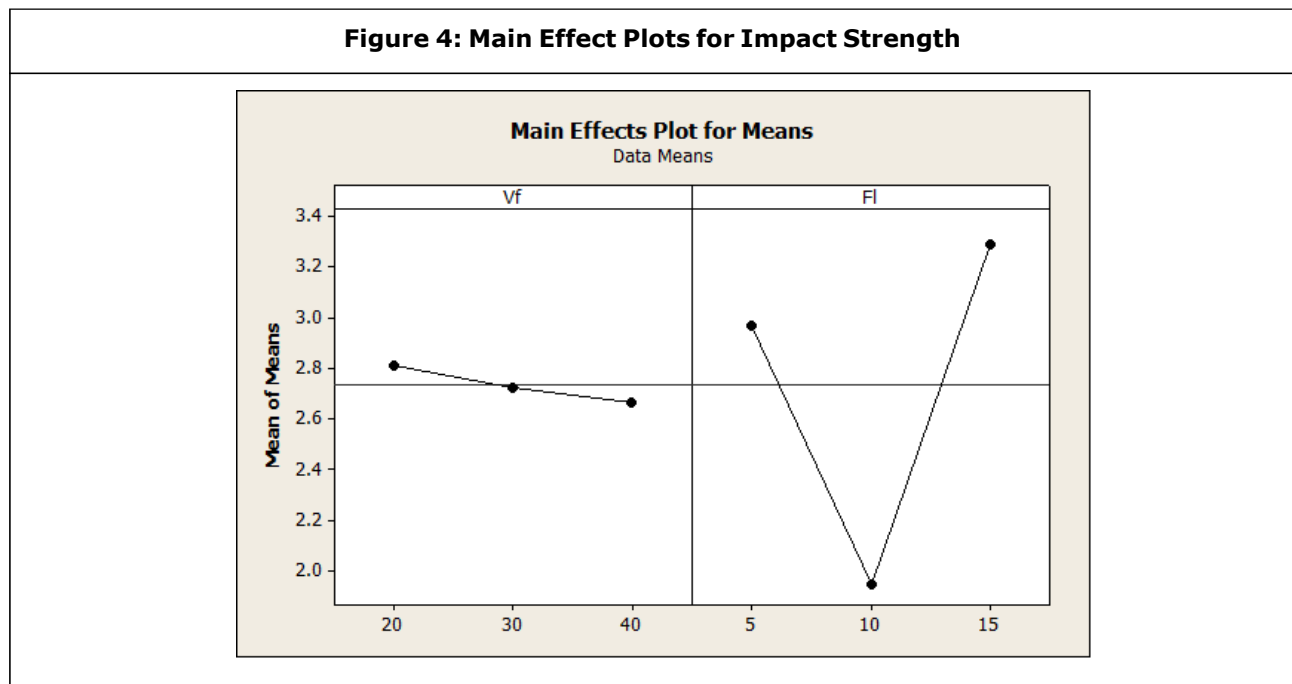


studied by using Table 7 and Figure 5. From the graph it is inferred that, the observed hardness of the composite material is high at low fiber length as compared to high fiber length. The experimental results indicated that the hardness of the composite material is higher at lower fiber length. From the response table is asserted that the fiber length is the main parameter which affect the hardness of the bamboo/glass fiber reinforced Hybrid composites.

For analyzing the influence of process parameters on mechanical properties of bamboo/glass fiber reinforced Hybrid composite material, Figure (6-14) shows the variation of mechanical properties like TS, FS, IS and hardness with respect to the constituent phases were drawn using response surface model observed. In each graph one variable is in variation and keeping the other variable constant at the middle level. From the graph 6, it is clearly seen that tensile strength of the composite material decreases with increase in the fiber weight fraction. In the present

investigation the maximum tensile strength of 78.9 Mpa was noticed for the composite material at the fiber weight fraction (Wf) of 20% and minimum tensile strength of 77.9 Mpa was noticed at fiber weight fraction of 40%. Figure 7 is a plot between tensile strength verses fiber length. From the graph it is asserted that the tensile strength of the composite material decreases with increase of fiber length (F<sub>l</sub>) up to 10 mm. However further increase in fiber weight fraction (Wf) increases the Tensile strength value. Maximum values of tensile strength of 130.2 Mpa were noticed at a fiber length of 15 mm and minimum tensile strength of 78.4 Mpa was noticed at a fiber length of 10 mm. Figure 8 is a plot of flexural strength Vs. fiber weight fraction. From the graph it is asserted that the flexural strength of the composite material increases with increase of fiber weight fraction. In the present investigation the maximum flexural strength of 374.8 Mpa was notice for the composite material at the fiber weight fraction (Wf) of 40% and minimum flexural

Table 7: Response Table for Hardness (Hn)		
Level	Fiber Volume Fraction(Vf)%	Fiber Length (Fl), mm
1	2.813	2.970
2	2.724	1.947
3	2.667	3.290
Delta	0.147	1.343
Rank	2	1

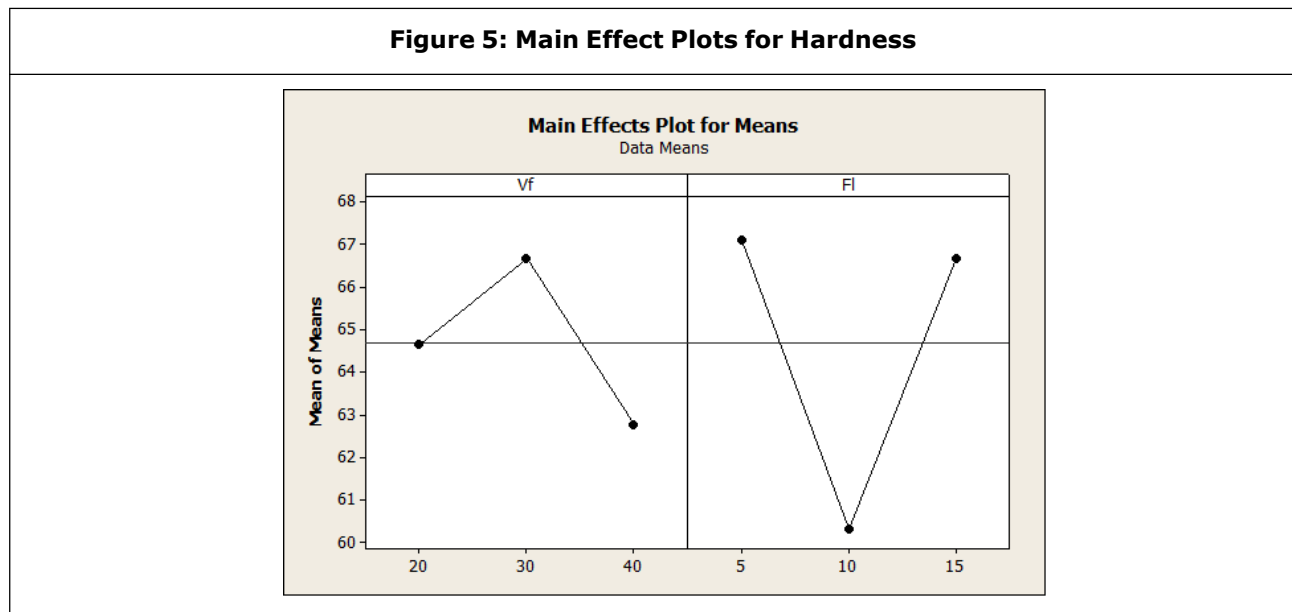


strength of 373.9 Mpa was noticed at fiber weight fraction (Wf) of 20%. Figure 9 the plot of variation of flexural strength with the fiber length (Fl). It is clearly seen from the graph the flexural strength of the composite material decreases with increase in fiber length. . In the present investigation the maximum flexural strength of 564.8 Mpa was notice for the composite material at the fiber length (F<sub>l</sub>) of 5 mm and minimum flexural strength of 303.9 Mpa was noticed at fiber length (F<sub>l</sub>) of 15 mm.

Figure 10 shows the variation of impact strength of the composite material with respect to fiber weight fraction.


From the graph it can be seen that the Impact

strength is decreasing with the increase in fiber weight fraction (Wf). In the present investigation the maximum impact strength of 2.327 KJ/m was notice for fiber weight fraction (Wf) of 20% and minimum impact strength of 2.324 K j/m was noticed for fiber weight fraction (Wf) of 40%. Figure 11 shows the plot between impact strength of the composite material verses fiber length (fl). From the graph it is clearly seen that Impact strength of the composite material decreases with increase in the fiber length. In the present investigation the maximum impact strength of 6.65 K j/m was notice for fiber length (fl) of 5 mm and minimum impact strength of 0.42 K j/m was

**Figure 6: Variation of Tensile Strength With Respect to Fiber Weight Fraction**

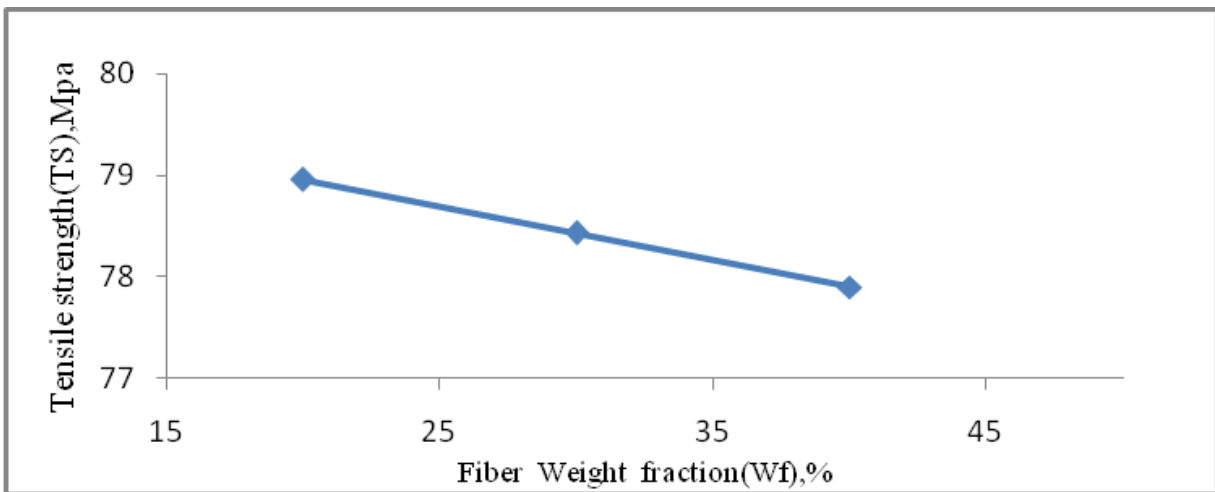

**Figure 7: Variation of Tensile Strength With Respect to Fiber Length Fraction**

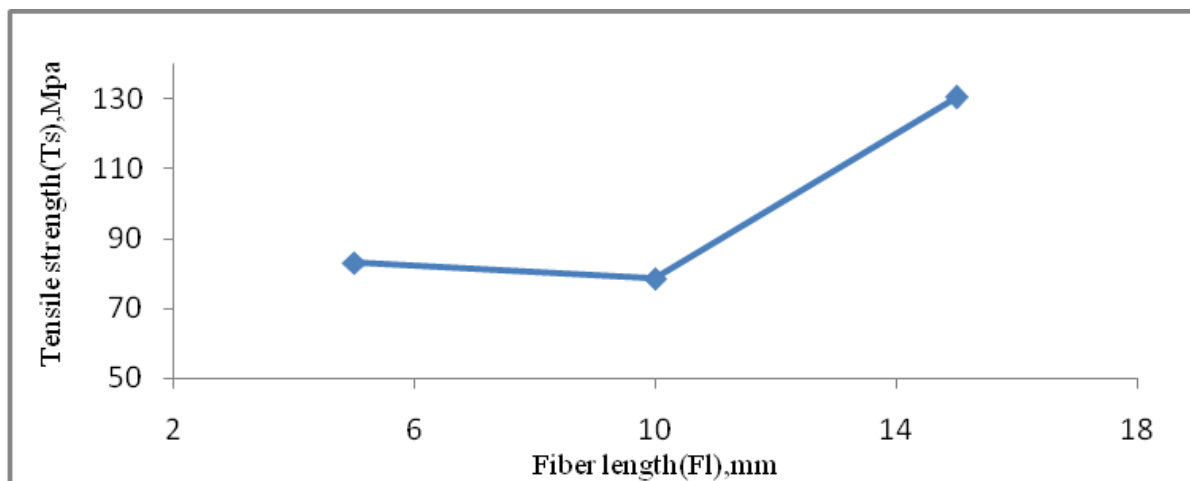


noticed for fiber length (fl) of 15 mm.


Figure 12 shows the plot between hardness of the composite material with respect to fiber weight fraction. From the graph it can be seen that the hardness of the composite material decreasing with the increase in fiber weight fraction (Wf) up to 30%. However further increase in fiber weight fraction (Wf) increases the hardness value. In the present investigation the maximum hardness value of 39.3 Mpa was notice

for fiber weight fraction (Wf) of 20% and minimum hardness value of 39.1 Mpa was noticed for fiber weight fraction (Wf) of 30%. Figure 13 shows the plot between hardness of the composite material with respect to fiber length (F<sub>l</sub>). From the graph it can be seen that the hardness of the composite material decreasing with the increase in fiber length (F<sub>l</sub>) to 10 mm. However further increase in fiber length (F<sub>l</sub>) increases the hardness value. In the present investigation the maximum hardness


**Figure 8: Variation of Flexural Strength with Respect to Fiber Weight Fraction**

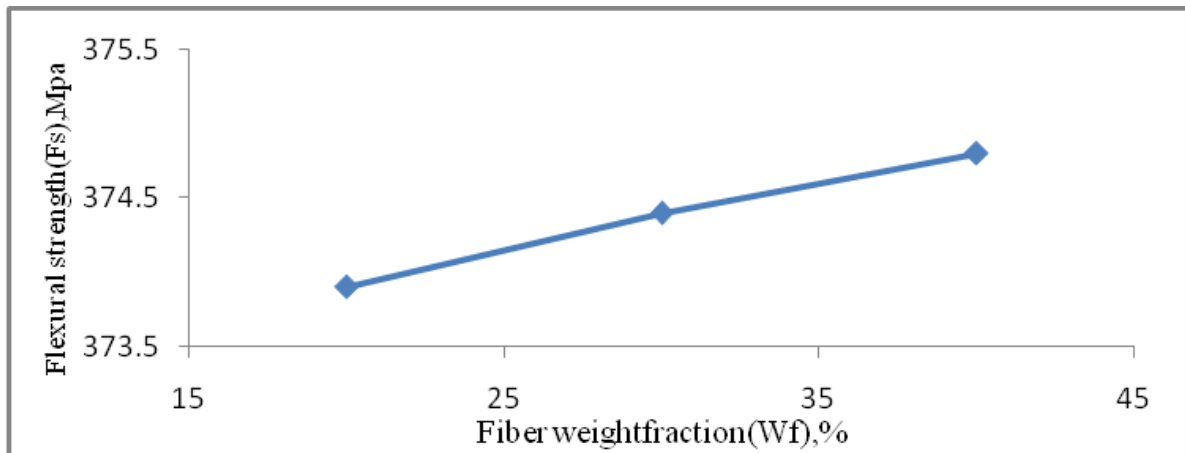


**Figure 9: Variation of Flexural Strength With Respect to Fiber Length**

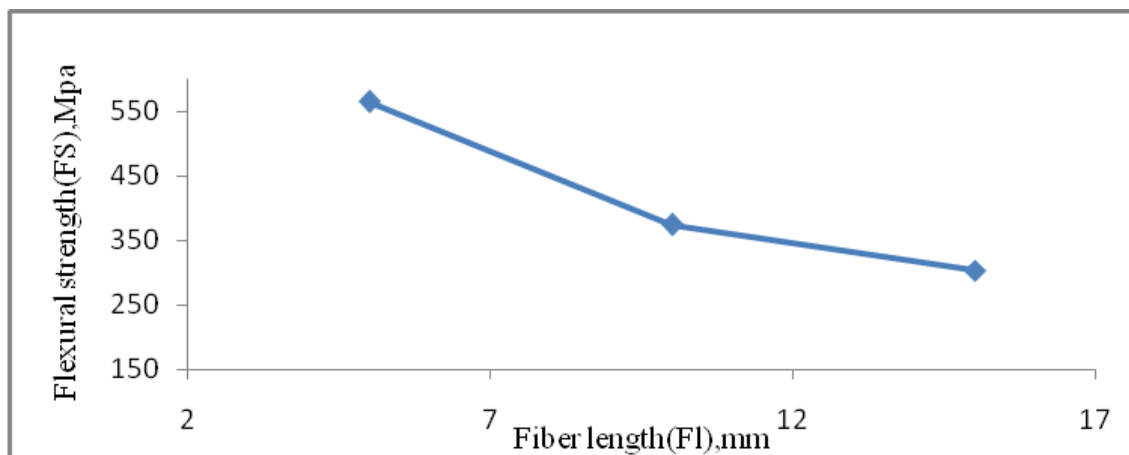


**Figure 10: Variation of Impact Strength With Respect to Fiber Weight Fraction**

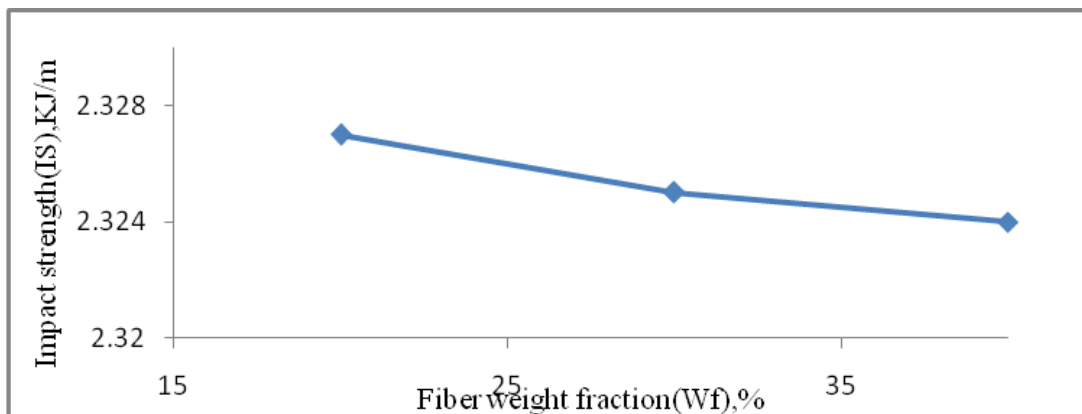


**Figure 11: Variation of Impact Strength With Respect to Fiber Length**

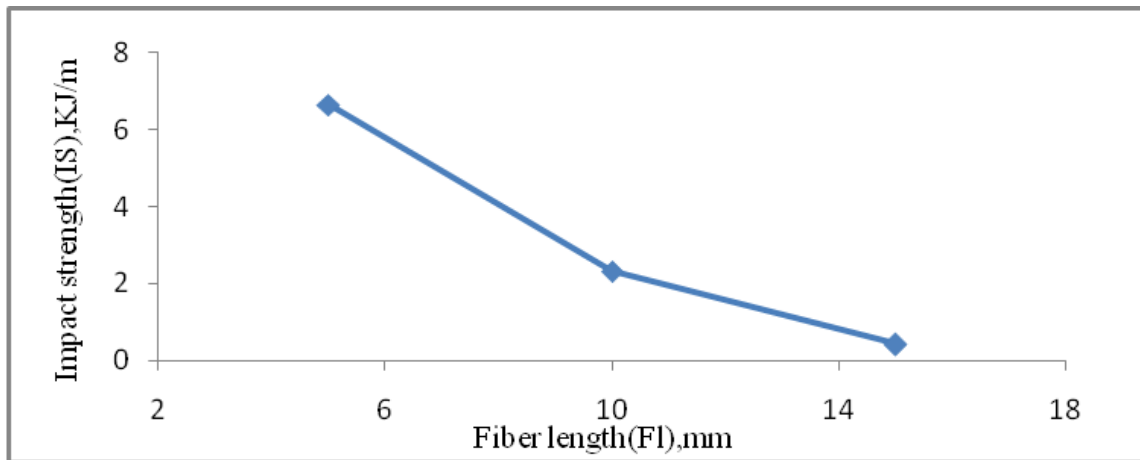

**Figure 12: Variation of Hardness Value With Respect to Fiber Weight Fraction**

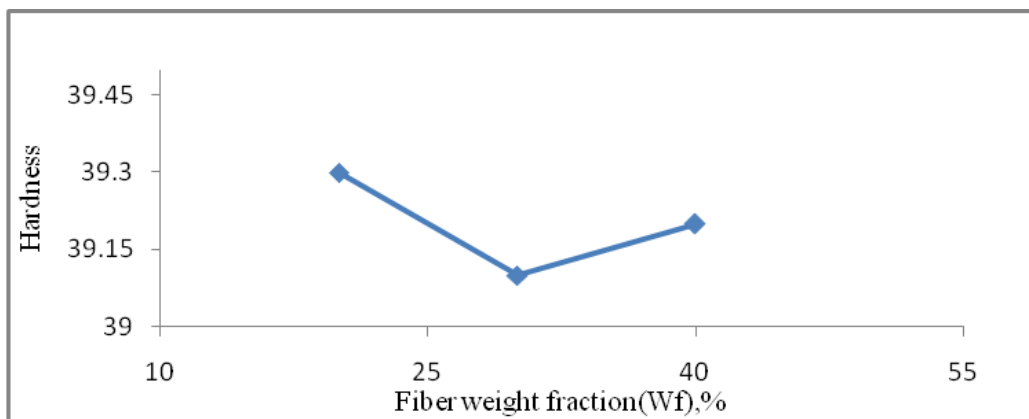

**Figure 13: Variation of Hardness Value With Respect to Fiber Length**

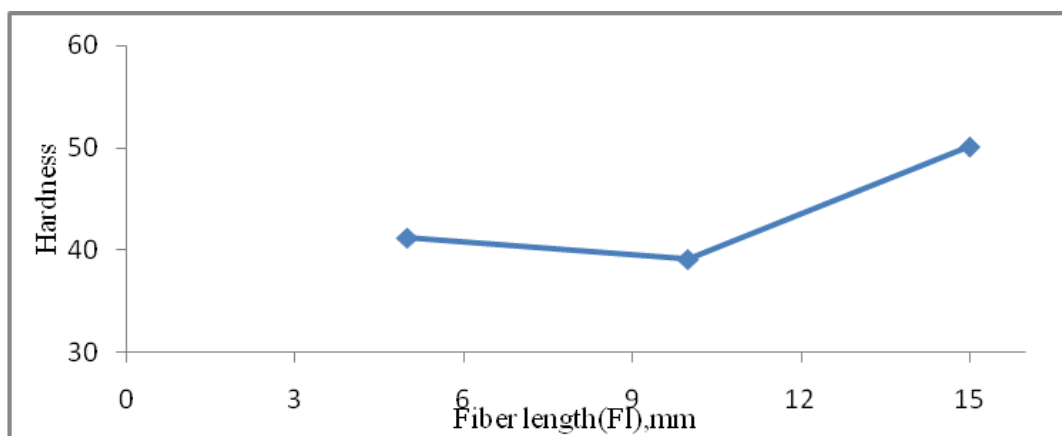

value of 50.1 was notice for fiber length (fl) of 15 mm and minimum hardness value of 39.1 was noticed for fiber length (fl) of 10 mm.

The modeling of processing parameters for evaluating the mechanical properties of green coconut fiber reinforced HDPE composite material has been carried out by Response Surface Methodology (RSM). The adequacy of the developed models has been varied through  $R^2$  values. The quantity  $R^2$  is called as coefficient of determination and is used to judge the adequacy of the model developed. The  $R^2$  value is the variability in the data accounted by the model in percentage as

$$R^2 = 1 - \frac{ss \text{ Error}}{ss \text{ total}}$$


where  $SS \text{ Error}$  is the sum of square error and  $SS \text{ total}$  is the sum of square total. The coefficient of determination is calculated using the above expression. In the present case, the coefficient of determination is 0.985 for tensile strength, 0.947 for flexural strength, 0.980 for impact strength and 0.952 for hardness, this shows high correlation

exists between experimental and predicted values. Hence, RSM model can be used effectively for the prediction of mechanical properties of bamboo/glass fiber reinforced composite material. Figures 14-17 shows Comparison between experimental values and RSM predicted values of mechanical properties like tensile strength, flexural strength and impact strength. From the graphs it is asserted that a close relationship exists between experimental values and predicted values.


### CHEMICAL RESISTANCE TEST

Figures (18-19) shows comparison of weight before immersion and after immersion in chemical for 24 hours. The results of chemical resistance shows that, there is lot of increase in weights of sample 1 and 6 when immersed in chemical of hydrochloric acid (HCl) and no loss/gain is observed in sample 8. When specimens are immersed in sodium carbonate solution ( $\text{Na}_2\text{CO}_3$ ), there are the slight changes in weights has been observed in except sample 8. When specimens are immersed in pure Acetic acid, then


**Figure 14: Comparison Between Experimental Values and RSM Predicted Values of Tensile Strength**

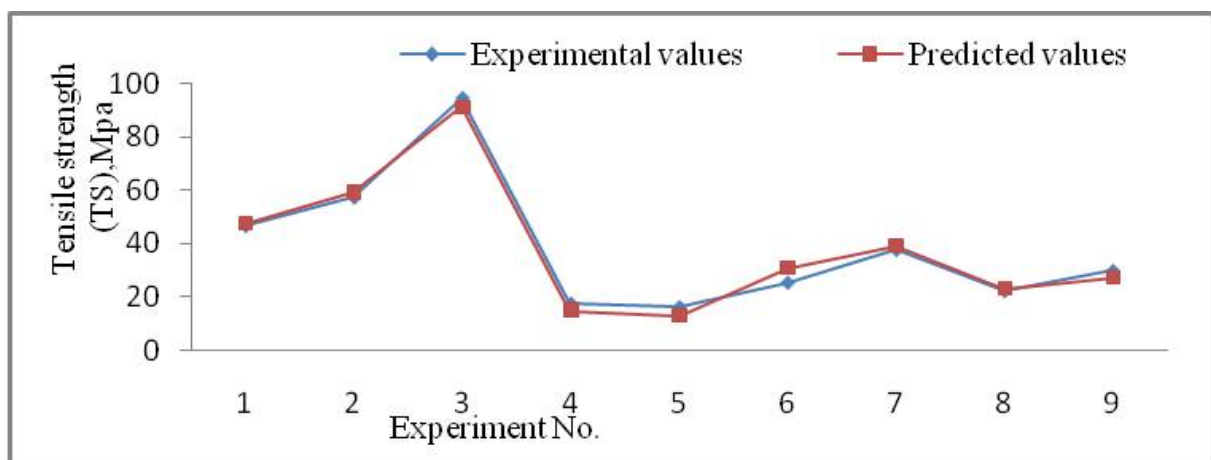


**Figure 15: Comparison Between Experimental Values and RSM Predicted Values of Impact Strength**

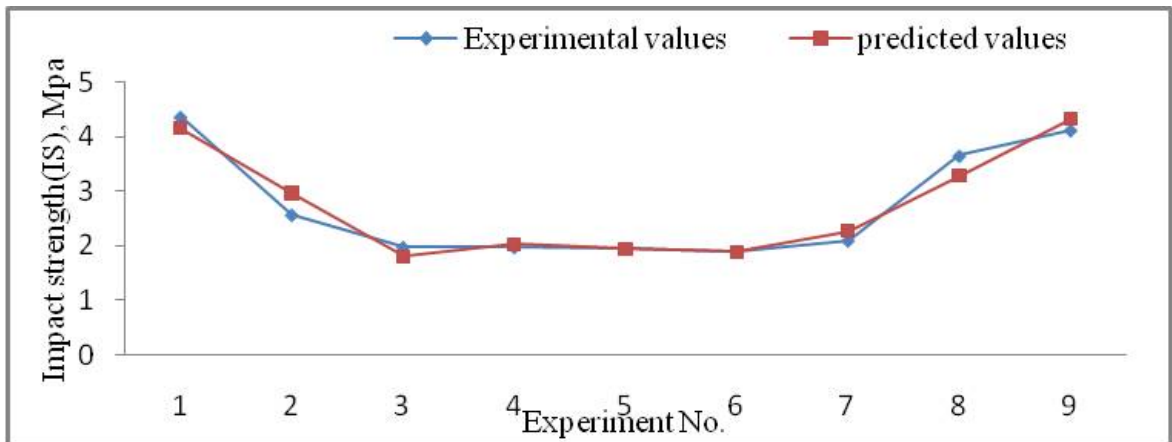

**Figure 16: Comparison Between Experimental Values and RSM Predicted Values of Flexural Strength**

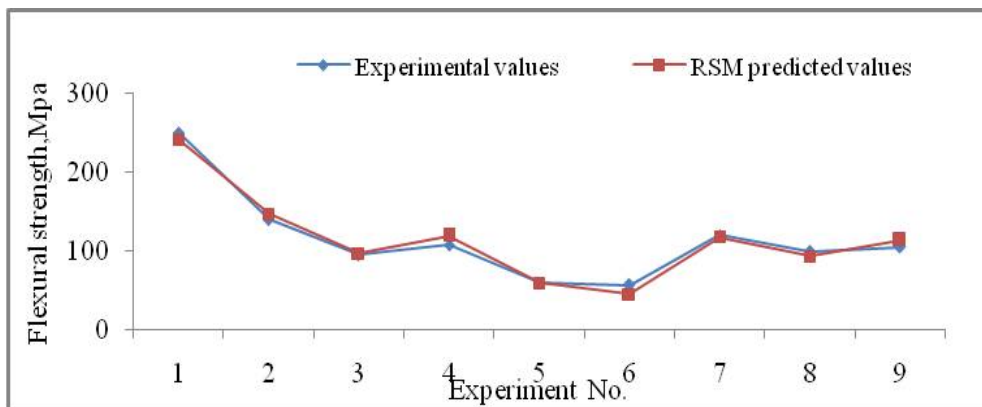


**Figure 17: Comparison Between Experimental Values and RSM Predicted Values of Hardness Strength**

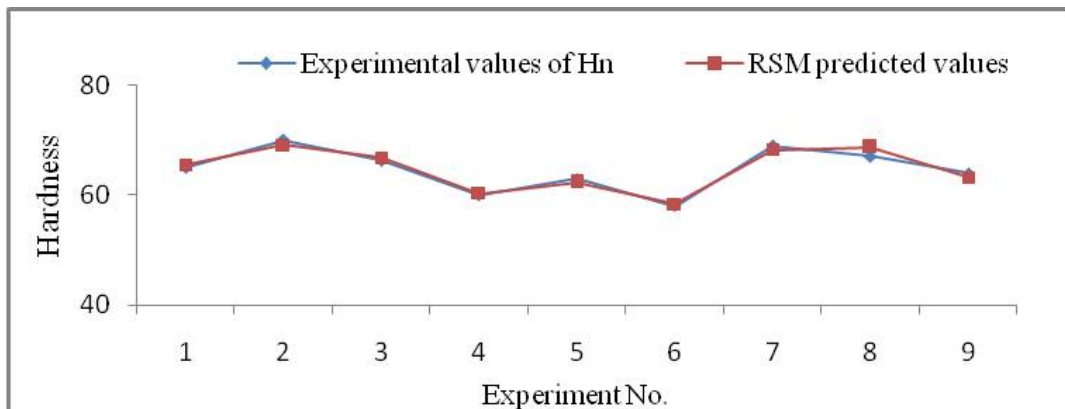




**Figure 18: Comparisons of Composite Weights Before and After Immersion**

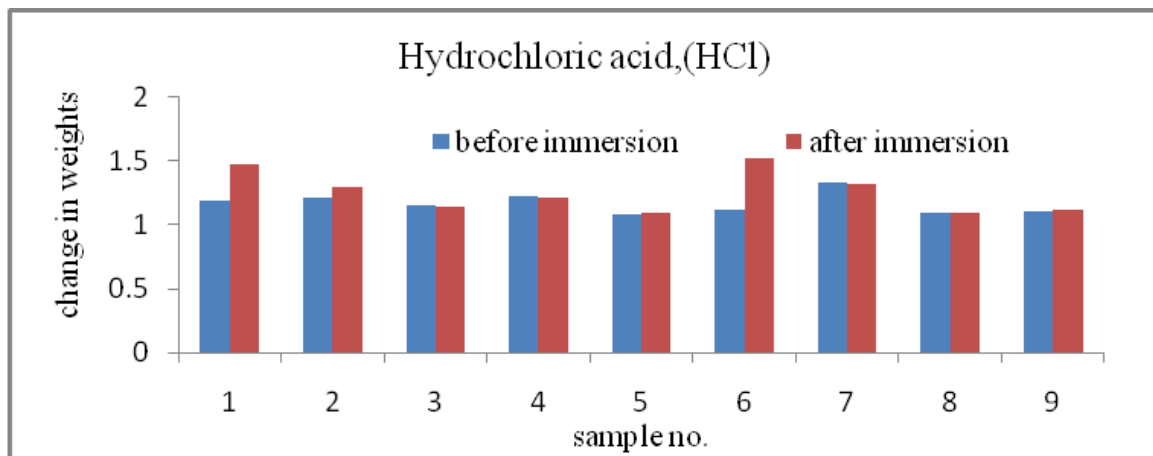

**Figure 19: Comparisons of Composite Weights Before and After Immersion**

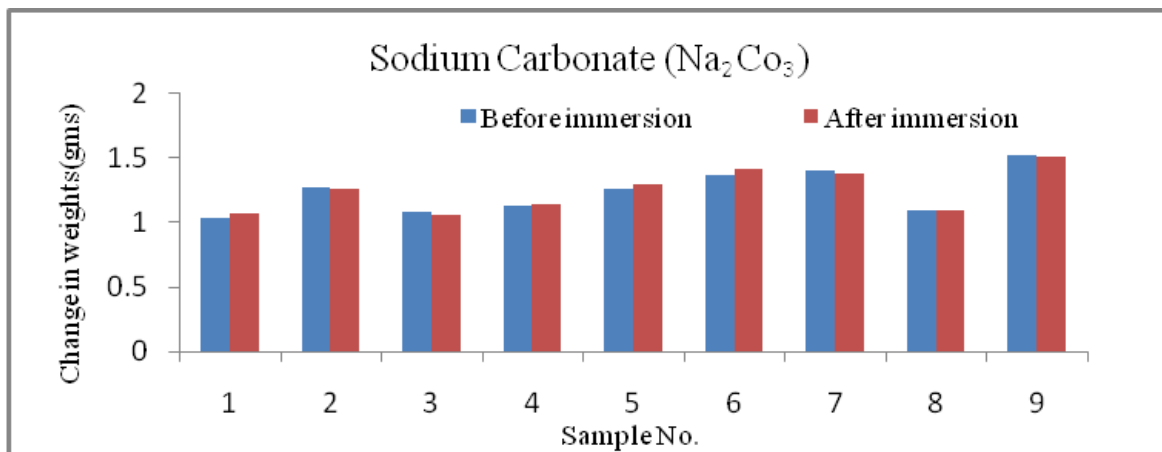

the all samples are decomposed because of both epoxy and acetic acid are organic in nature. So they dissolved in each other. From this observation it is concluded that, the epoxy based composites should be kept away from the organic solutions.

**CONCLUSION**

The hybrid composites were prepared in order to characterize the four mechanical properties, viz., Tensile strength, Impact strength, Flexural

strength and hardness and also an attempt is made to check the affinity of the hybrid composite towards chemical resistance. Based on the experimental results, the following conclusions are drawn within the range of parameters selected.

Response surface methodology is found to be successful for modeling and analysis of mechanical properties of hybrid composite materials with respect to various combinations

of design variables (Fiber length and Fiber volume fraction).

- Tensile strength of the hybrid composite material decreases with the increase of fiber loading fraction.
- Tensile strength of the hybrid composite material decreases with the increase of fiber length up to 10 mm there after rapidly increases with increase of fiber length.
- Flexural strength of hybrid composite materials linearly increases with increase in fiber weight fraction and its value goes on decreasing with increase of fiber length 5 to 15 mm.
- Impact strength of the hybrid composite material slightly decreases with increase in weight fraction and rapidly decreases with increase of the fiber length.
- Hardness of the hybrid composite material rapidly decreases with increase of fiber weight fraction up to 30% then after increases slightly with increase in fiber weight up to 40% and the hardness of the composite slightly decreases with increase in the fiber length up to 10 mm, then after it increases rapidly with increase in fiber length up to 15 mm.
- The developed second order response surface model can be used to predict the mechanical properties of hybrid composites within the chosen range with 95% confidence intervals. Using such models, one can obtain remarkable saving in time and cost.
- The hybrid composite materials with higher fiber length and moderate fiber weight fraction are least affected by Hydrochloric acid.

- The hybrid composite material is least affected by sodium carbonate ( $\text{Na}_2\text{CO}_3$ )
- From the experiment results it is concluded that the epoxy based composite should kept away from the organic solutions.

## ACKNOWLEDGMENT

It is my privilege to express my thanks to my guide Dr. Syed Altaf Hussain, M.Tech, Ph.D., Professor in Mechanical Engineering, R G M College of Engineering and Technology, for his valuable guidance and encouragement.

## REFERENCES

1. Syed Altaf Hussain and V Pandurangadu (2012), "Mechanical properties of green coconut fiber reinforced HDPE polymer composite".
2. Syed Altaf Hussain and V Pandurangadu (2012), "Mechanical properties of short bamboo fiber reinforced polyester composites filled with alumina particulate".
3. Raghavendra Rao H, Ashok Kumar M G and Ramachandra Reddy (2011), Hybrid composites: Effects of fibers on Mechanical properties.
4. Ashok Kumar M, Ramachandra Reddy G, Siva Bharathi Y, Venkata Naidu S and Naga Prasad Naidu V (2010), "Frictional Co-efficient, Hardness, Impact Strength, and Chemical Resistance of Reinforced Sisal/ Glass Fiber Epoxy Hybrid Composites", *Journal of Composite Materials*, (accepted).
5. Venkata Reddy G, Venkata Naidu S and Shobha Rani T (2008), "Kapok/glass polyester hybrid composites: tensile and hardness properties", *J. Rein. Plast. Comp.*,

Vol. 27, pp. 1775-1787.

6. Noorunnisa Khanam P, Mohan Reddy M, Raghu K, John K and Venkata Naidu S (2007), "Tensile, flexural and compressive properties of sisal/silk hybrid composites", *J. Rein. Plast. Comp.*, Vol. 26, pp. 1065-1075.
7. Raghu K, Noorunnisa Khanam P and Venkata Naidu S (2008), "Chemical resistance studies of silk/sisal fiber reinforced unsaturated polyester-based hybrid composites", *J. Rein. Plast. Comp.*, Vol. 27, pp. 1-3.
8. Noorunnisa Khanam P, Ramachandra Reddy G, Raghu K and Venkata Naidu S (2009), "Tensile, flexural, and compressive properties of coir/silk fiber-reinforced hybrid composites", *J. Rein. Plast. Comp.*, pp. 1-4.
9. Ismail H, Freakley P, Sutherland I K and Sheng E (1995), "Effect of multifunctional additives on mechanical properties of silica filled natural rubber compound", *Euro. Polymer. J.*, Vol. 11, pp. 1109-1117.
10. Sim L C, Lee C K, Raman S R and Ismail H (2006), "Cure characteristics and mechanical and thermal properties of Al<sub>2</sub>O<sub>3</sub> and ZnO reinforced silicon rubber", *Polym. Plast. Technol. Eng.*, Vol. 45, pp. 1-7.



**International Journal of Engineering Research and Science & Technology**

**Hyderabad, INDIA. Ph: +91-09441351700, 09059645577**

**E-mail: editorijerst@gmail.com or editor@ijerst.com**

**Website: www.ijerst.com**

